

Competition between magnetism and superconductivity in the organic metal

κ -[BEDT-TTF]₂Cu[N(CN)₂]Br

David Fournier, Mario Poirier, and Kim Doan Truong
*Regroupement Québécois sur les Matériaux de Pointe, Département de Physique,
 Université de Sherbrooke, Sherbrooke, Québec, Canada J1K 2R1*

(Dated: February 6, 2008)

Ultrasonic velocity and attenuation measurements on the quasi-two-dimensional organic conductor κ -[BEDT-TTF]₂Cu[N(CN)₂]Br give the first determination of the coexistence zone of the antiferromagnetic and superconducting phases which extends deep in the metallic part of the pressure-temperature phase diagram of these salts. This zone is identified from a precise control of the ordering in ethylene end groups which acts as an internal pressure. The two phases are found to compete whereas superconducting fluctuations begin to contribute to the attenuation at 15 K, namely at the onset of magnetic order that is well above the superconducting transition temperature $T_c = 11.9$ K. Finally, the temperature profile of sound attenuation for both longitudinal and transverse phonon polarizations is found to be inconsistent with a conventional s -wave order parameter.

PACS numbers: 74.70.Kn, 74.25.Ha, 74.25.Ld

The physics of strongly correlated materials in the vicinity of the Mott transition has motivated much interest over the last decade[1]. Vanadium oxides, manganites, frustrated quantum magnetic insulators, high- T_c and organic superconductors are examples of such systems where complex orders and quantum criticality can be found. More specifically, the coexistence and/or competition of magnetism and superconductivity near the Mott transition in high- T_c and organic materials constitute fundamental issues that are widely addressed in the literature (ex. [2]). In this respect the layered quasi-two-dimensional κ -[BEDT-TTF]₂X compounds are of great interest. Their generic temperature vs pressure phase diagram [3, 4, 5, 6] reveals that the superconducting (SC) and the antiferromagnetic insulating phases (AF) are separated by a first order Mott transition line (MI), where a microscale phase separation takes place [7]. The first order line persists in the paramagnetic phase and terminates with a critical point, from which a pseudogap line emerges under pressure as a precursor of the superconducting state. κ -[BEDT-TTF]₂X compounds can thus be considered as prototype systems to study the interplay between magnetic and superconducting phases in the close proximity of a first order MI transition

In this work the ultrasonic technique and thermal cycling are used to present a detailed study of the different phases appearing in the vicinity of the Mott transition line in the κ -[BEDT-TTF]₂Cu[N(CN)₂]Br compound (noted κ -H₈-Br hereafter). At ambient pressure, κ -H₈-Br is located on the metallic side of the MI line and a slight shift on the pressure scale can be achieved by a fine thermal tuning of residual intrinsic disorder related to ordering of ethylene end groups of BEDT-TTF molecules occurring between 200 and 60 K [8]. Although a larger shift could be obtained by partial alloying with the Cu[N(CN)₂]Cl anion and/or from deuteration of the BEDT-TTF molecules, these procedures introduce, however, extrinsic disorder that must be avoided. Here, we report sound velocity and the first ultrasonic attenuation

measurements to be realized on these layered compounds. The results clearly establish a wide domain of the P-T phase diagram where magnetic and superconducting ordered phases overlap. A fine tuning of ethylene disorder through thermal cycles is found to move the system on the pressure scale. The MI is thus reached from the metallic side where the emergence of an ordered magnetic phase is found, which is detrimental to superconductivity. The magnetic phase that set in around 15 K in κ -H₈-Br scales with the amplitude of the pseudogap anomaly above 30 K or so[5]. As for the superconducting transition occurring at 11.9 K, fluctuation effects are found few degrees above the critical temperature.

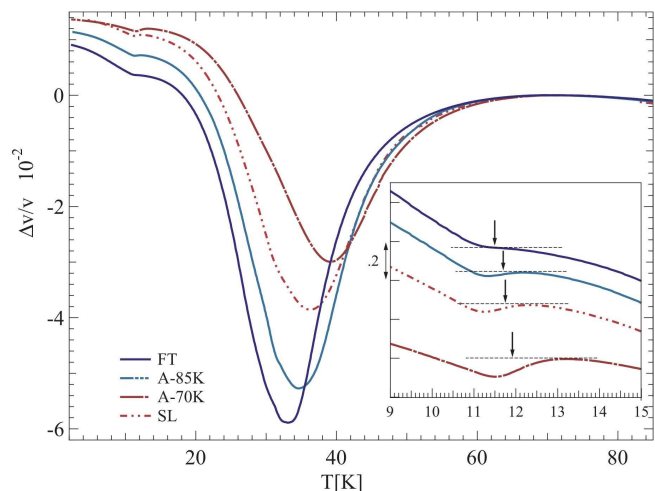


FIG. 1: Relative variation of the longitudinal L[010] velocity at 160 MHz as a function of temperature for different thermal cycles. Inset: zoom around the 12 K anomaly; the curves have been shifted for a better view. The arrows indicate the maximum slope which determines T_c .

Although difficult to adapt to thin organic crystals, pulsed ultrasonic velocity experiments have already been carried out on few compounds of this family [5, 9, 10]. It

consists in measuring the phase shift and the amplitude of the first elastic pulse transmitted through the crystal and a delay line [10]; this is why the technique yields only velocity and attenuation variations. Because of the platelet shape of the selected κ -H₈-Br crystals, only elastic waves propagating perpendicularly to the plane (direction (010)) could be generated with small piezoelectric transducers. Longitudinal waves polarized along the b axis L[010] and, for the first time, transverse waves polarized along the a axis T[100] could be generated over the 30-450 MHz frequency range. The crystals were submitted to the following thermal cycles from 200 K to 2 K: the standard slow cool (SL) process, 10 K/hour, and a fast cool (FT) process during 10 minutes; following a FT process, a 24 hour annealing at 85 K (A-85K) or 70 K (A-70K). According to the literature [8, 11, 12], maximum order of the ethylene end groups is obtained when annealing is performed at a temperature between 60 and 80 K for a period of 24 hours. All the ultrasonic data presented in this paper were obtained when sweeping the temperature up from 2 K. A magnetic field up to 16 Tesla could be applied perpendicularly to the plane in order to completely eliminate the superconducting state.

We report in Figure 1 the temperature profile of the relative velocity variation ($\frac{\Delta v}{v}$) of the L[010] mode at 160 MHz over the 2-80 K range for different thermal cycles. No frequency dependence is observed over the 30-450 MHz range; only the signal to noise ratio increases with frequency. The profiles reveal two distinct anomalies: i) a huge dip (3-6%) just above 30 K previously associated to a compressibility increase driven by the magnetic fluctuations of the electronic degrees of freedom at the pseudogap [5]; ii) a much smaller anomaly around 12 K likely related to the onset of superconductivity. Both the amplitude and the position of the compressibility anomaly are highly dependent on the amount of disorder: FT (maximum disorder) yields the maximum amplitude (6%) at the lowest temperature (33 K), whereas SL followed by annealing at 70 K (minimum disorder) reduces by half the anomaly and shifts it to higher temperature (39 K). Other cooling rates give intermediate disorder and in turn intermediate results. The process of ordering the ethylene end groups thus mimics an actual increase of the effective pressure [10]. The effect of disorder on the small 12 K anomaly is shown in the inset of Figure 1. Fast cooling (maximum disorder) produces a mere change of slope just above 11 K while a small dip grows progressively with increasing order together with a small shift to higher temperatures. This dip signals the onset of the superconducting state in agreement with what is expected for a longitudinal mode [13]. However, the increase of T_c with internal pressure (see inset of Fig.1), confirmed by SQUID magnetization measurements, is not consistent with hydrostatic pressure studies. This might be explained by small residual disorder to which non s -wave superconductivity is particularly sensitive. An important hysteresis is also observed on the velocity data (also true for the attenuation presented later) when the tem-

perature is swept up and down between 2 K and 20 K, which is consistent with the proximity of the first order MI transition.

As superconductivity is easily quenched by a field perpendicular to the highly conducting planes ($H_{c2}^\perp \sim 12$ Tesla), a magnetic field investigation of the low temperature anomaly appears appropriate to identify the different phases. The longitudinal L[010] mode and a transverse mode, T[100], which appears to couple more strongly to the superconducting state, are used for this investigation. We compare in Figure 2(a) the $\frac{\Delta v}{v}(T)$ data at 0 and 16 Tesla for the FT process (maximum disorder). In zero field, the velocity of the L[010] mode shows

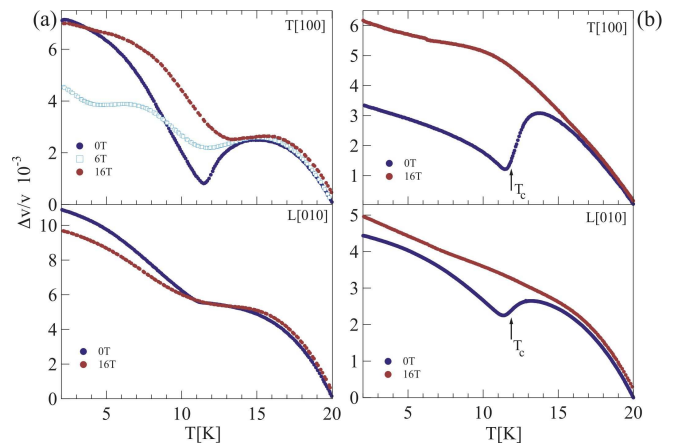


FIG. 2: Relative variation of sound velocity as a function of temperature at fixed magnetic field values: L[010] mode at 100 MHz and T[100] mode at 160 MHz. (a) FT process (maximum disorder) and (b) A-70K process (maximum order).

a plateau around 15 K before increasing further below 11 K, where a marked softening of the mode is produced by the magnetic field. For the T[100] mode, the velocity shows a similar plateau around 15 K, followed by an important dip centered at 11.5 K. The dip disappears in a 16 Tesla field but the plateau is maintained. We thus conclude that the 11.5 K dip and the 15 K plateau signal respectively superconductivity and another ordered phase. This is confirmed by the 6 Tesla curve of Figure 2(a), which shows the shift of the 11.5 K anomaly to 5 K, whereas the plateau at 15 K is kept unchanged. When maximum order (A-70K process) is achieved, the temperature profile of the anomaly is greatly modified (Fig. 2(b)). When the temperature decreases from 20 K in zero magnetic field, a maximum is observed around 13.5 K followed by a sharp drop till a minimum is achieved at 11.5 K; at lower temperatures the velocity increases smoothly. The amplitude and temperature profile of the anomaly are however different for both acoustic modes, being more pronounced for the T[100] one. A 16 Tesla field completely suppresses the anomaly: the velocity increases smoothly with decreasing temperature and, in contrast to the FT process, no plateau is observed at 15 K; only a weak variation of slope occurs around 8 K. Minimizing

disorder then favors the superconducting phase as signaled by the sharp drop centered at 11.9 K consistent with the $\Delta v/v$ data (inset Fig.1). We cannot, however, discard contributions of other phases, which can produce small slope variations. The presence and nature of these phases are most easily revealed by the attenuation measurements whose sensitivity increases with frequency. We report now the first ultrasonic attenuation measurements realized on this family of layered conductors for the A-70K process, which favors superconductivity.

We present in Figure 3 the variations of the attenuation $\Delta\alpha(T)$ obtained simultaneously with the $\frac{\Delta v}{v}(T)$ data. The zeroth value is arbitrarily chosen by extrapolating the zero field curve at 0 K. For both ultrasonic

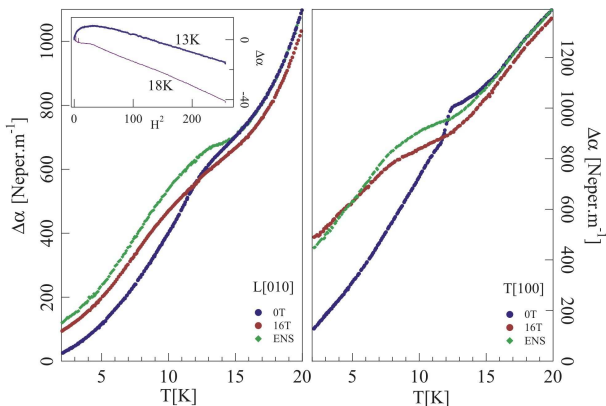


FIG. 3: Variation of the sound attenuation as a function of temperature for the A-70K process (maximum order) at fixed magnetic field values: L[010] mode at 160 MHz and T[100] at 100 MHz. See text for the description of the ENS curve. Inset: $\Delta\alpha$ as a function of H^2 at 13 K and 18 K for the L[010] mode at 160 MHz.

modes over the 2-20 K temperature range, $\Delta\alpha(T)$ is an increasing function of temperature due to a large attenuation peak accompanying the huge velocity dip near 40 K (Fig.1)[5]. In zero field, the rate of increasing attenuation is reduced at the superconducting temperature around 12 K; this trend is more pronounced for the T[100] mode, where it almost appears as a discontinuity in the slope. In a 16 Tesla field, a substantial increase of $\Delta\alpha$ is produced below T_c when superconductivity is quenched, while a weak decrease is observed above. These effects are again more pronounced for the T[100] mode. Surprisingly, a change of slope persists below 15 K which implies the coexistence of a secondary phase with superconductivity even when disorder is minimized. To get an insight into this phase and to isolate the superconducting contribution to the attenuation, we now examine precisely the field dependence of the attenuation.

The $\Delta\alpha(T)$ data vary quadratically with field (inset of Figure 3) over the 2-20 K range as long as $H > H_{c2}^\perp$. Such a H^2 dependence, which is also observed for the velocity data, proceeds from the first correction term to transport and magnetic properties to which ultrasonic waves couple [14, 15, 16, 17, 18]. If we write $\Delta\alpha(T)$

in zero field as a sum of two contributions, one due to the superconducting state (SC) and another one to an *exotic normal state* (ENS), $\Delta\alpha(T) = \Delta\alpha_{SC}(T) + \Delta\alpha_{ENS}(T)$, we can isolate the SC contribution by modeling the field effects on the ENS phase in the following way: $\Delta\alpha_{ENS}(T, H) = \Delta\alpha_{ENS}(T, 0) + \gamma_\alpha(T)H^2$. Thus, plots of $\Delta\alpha$ as a function of H^2 at fixed temperatures yield $\gamma_\alpha(T)$ as the slope and $\Delta\alpha_{ENS}(T, 0)$ as the extrapolated value toward the zero field limit. The contribution of the SC phase $\Delta\alpha_{SC}(T)$ is thus obtained after subtracting the ENS contribution.

When compared with zero field data (Figure 3), the $\Delta\alpha_{ENS}(T, 0)$ curves do not appear monotonous. When the temperature is decreased from 20 K, the ENS curves for both modes coincide with the zero field one but they depart abruptly from each other around 15 K. For $T < 15$ K, apart from the 12-15 K temperature range for the T[100] mode, the ENS attenuation is higher than in zero field, in agreement with larger sound attenuation in the normal state compared to the superconducting one. Anomalous behaviors at 15 K can also be seen in the $\gamma_\alpha(T)$ and $\gamma_v(T)$ coefficients. Examples of such coefficients for the L[010] mode are presented in the inset of Figure 4 at a frequency of 428 MHz, which yields maximum sensitivity. Below 20 K, the $\gamma_\alpha(T)$ coefficient increases with decreasing temperature until an abrupt downward transition occurs at 15 K; $\gamma_v(T)$ is rather constant below 20 K, but it increases steeply at 15 K with a quasi-linear variation at lower temperatures. These features of the ENS phase mimic the onset of an antiferromagnetic order parameter at 15 K that is 3 K above the superconducting transition. This is consistent with studies where deuteration of the BEDT-TTF molecules shifts the compound on the pressure scale at the boundary of the phase diagram where superconductivity is replaced by an antiferromagnetic insulating phase at 15 K [19]. We suggest that the 15 K anomalies observed in our velocity and attenuation data are the result of a magneto-elastic coupling with an ordered AF phase. The temperature at which this phase occurs is $T_{AF} = 15$ K, and appears to be very weakly field dependent (Fig. 2a) up to 16 Tesla. This observation is consistent with the symmetry of the AF phase deduced for the κ -D₈-Br compound [20].

Finally, the contribution of the superconducting state to the attenuation $\Delta\alpha_{SC}(T)$ is presented in Figure 4. For both modes, $\Delta\alpha_{SC}(T)$ is negative as expected for a superconducting state. However, the temperature profile below T_c does not appear to be consistent with a conventional *s*-wave order parameter for which a monotonous decrease of attenuation is well known to be expected. For the L[010] mode, the decrease of the attenuation at 15 K suggests the existence of superconducting fluctuations whereas the shoulder at 11.9 K coincides with the onset of phase coherence. Then $\Delta\alpha_{SC}(T)$ goes through a minimum around 8 K before increasing further down to 2 K, while remaining always negative. For the transverse mode T[100], although superconducting fluctuations are also effective below 15 K, they rather produce an en-

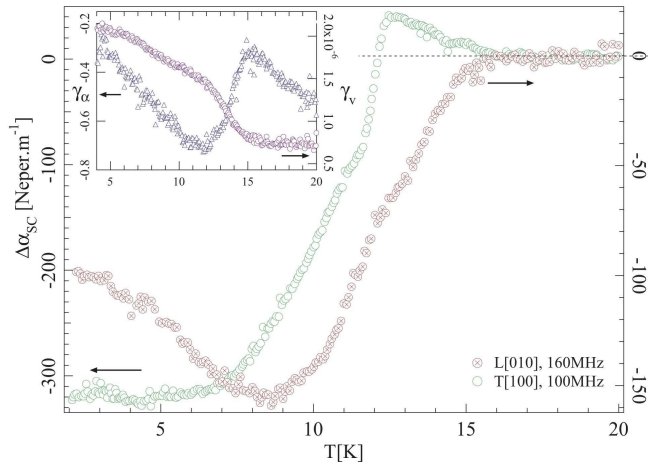


FIG. 4: $\Delta\alpha_{SC}$ as a function of temperature: L[010] mode at 160 MHz and T[100] at 100 MHz. Inset: Parameters $\gamma_v(T)$ and $\gamma_\alpha(T)$ of the ENS for the L[010] mode at 428MHz.

hancement of the attenuation followed by a sharp downward trend below 12.5 K and a further change of slope at $T_c = 11.9$ K. At lower temperatures $\Delta\alpha_{SC}(T)$ decreases further and flattens below 7 K. These features around 7-9 K cannot be reconciled with any theoretical model for the moment, although we must keep in mind the peculiar topology of the Fermi surface, which consists of two parts, namely the quasi-one-dimensional electron sheets and two-dimensional hole pockets. We remind that the ultrasonic L[010] mode probes the complete 2D Fermi surface while the transverse T[100] one is mainly sensitive to the 1D electron sheets. Finally, there may be a connection between these low temperature features around 8 K with a secondary dissipation phase observed in the pressure transport measurements[3, 21].

In summary, our velocity and attenuation data point clearly toward a competition between metallic (superconducting) and insulating (antiferromagnetic) phases at low temperatures deep in the Fermi liquid part of the P-T phase diagram. The farther the system is from the first order boundary, the stronger is the superconducting phase relative to the magnetic one. This can be realized by applying hydrostatic pressure or, as demonstrated in our paper, by controlling the amount of disorder of the ethylene end groups. This competition is summarized in Figure 4: when magnetic fluctuations probably connected to an ordered AF phase disappear around 15 K, superconducting fluctuations grow rapidly to yield a transition at 11.9 K. It is clearly demonstrated that disorder favors the magnetic fluctuations (huge dip at 33 K) which is detrimental to the superconducting state. However, this competition apparently yields a phase separation over all the sample's volume as it was suggested from infrared reflectivity data at high temperatures [22] and confirmed by the hysteresis observed on our velocity and attenuation data in the 2-20 K range. Finally, although the attenuation data does not appear consistent with a *s*-wave order parameter, a thorough frequency and polarization analysis of the ultrasonic attenuation together with precise theoretical predictions [23] will be needed to establish the symmetry of the superconducting order parameter.

The authors thank C. Bourbonnais, A.-M. Tremblay for discussions and the critical reading of the manuscript and M. Castonguay for his technical support. This work was supported by grants from the Fonds Québécois de la Recherche sur la Nature et les Technologies (FQRNT) and from the Natural Science and Engineering Research Council of Canada (NSERC)

-
- [1] F. Kagawa, K. Miyagawa, and K. Kanoda, *Nature* **436**, 534 (2005).
 - [2] R. I. Miller, R. F. Kieff, J. H. Brewer, F. Callaghan, J. E. Sonier, R. Liang, D. A. Bonn and W. Hardy, *Phys. Rev. B* **73**, 144509 (2006).
 - [3] H. Ito, T. Ishiguro, M. Kubota, and G. Saito, *J. Phys. Soc. Jpn.* **65**, 2987 (1996).
 - [4] S. Lefebvre, P. Wzietek, S. Brown, C. Bourbonnais, D. Jérôme, C. Mézière, M. Fourmigué, and P. Batail, *Phys. Rev. Lett.* **85**, 5420 (2000).
 - [5] D. Fournier, M. Poirier, M. Castonguay, and K. Truong, *Phys. Rev. Lett.* **90**, 127002 (2003).
 - [6] P. Limelette, P. Wzietek, S. Florens, A. Georges, T. A. Costi, C. Pasquier, D. Jérôme, C. Mézière, and P. Batail, *Phys. Rev. Lett.* **91**, 016401 (2003).
 - [7] T. Sasaki, N. Yoneyama, N. Kobayashi, Y. Ikemoto, and H. Kimura, *Phys. Rev. Lett.* **92**, 227001 (2004).
 - [8] M. A. Tanatar, T. Ishiguro, T. Kondo, and G. Saito, *Phys. Rev. B* **59**, 3841 (1999).
 - [9] K. Frikach, P. Fertey, M. Poirier, and K. Truong, *Synth. Met.* **103**, 2081 (1999).
 - [10] K. Frikach, M. Poirier, M. Castonguay, and K. D. Truong, *Phys. Rev. B* **61**, R6491 (2000).
 - [11] M. Pinteric, S. Tomic, M. Prester, D. Drobac, and K. Maki, *Phys. Rev. B* **66**, 174521 (2002).
 - [12] J. Müller, M. Lang, F. Steglich, J. A. Schlueter, A. M. Kini, and T. Sasaki, *Phys. Rev. B* **65**, 144521 (2002).
 - [13] L. R. Testardi, *Phys. Rev. B* **12**, 3849 (1975).
 - [14] M. S. Steinberg, *Phys. Rev.* **110**, 772 (1958).
 - [15] S. Rodriguez, *Phys. Rev.* **130**, 1778 (1963).
 - [16] M. Tachiki, and S. Maekawa, *Prog. Theor. Phys.* **21**, 1 (1974).
 - [17] S. Maekawa, and M. Tachiki, *Prog. Theor. Phys.* **58**, 787 (1977).
 - [18] S. Maekawa, S. Takahashi, and M. Tachiki, *Prog. Theor. Phys.* **59**, 23 (1978).
 - [19] A. Kawamoto, K. Miyagawa, and K. Kanoda, *Phys. Rev. B* **55**, 14140 (1997).
 - [20] K. Miyagawa, A. Kawamoto, and K. Kanoda, *Phys. Rev. Lett.* **89**, 017003 (2002).
 - [21] H. Ito, T. Ishiguro, T. Kondo and G. Saito, *J. Phys. Soc. Jpn.* **69**, 290 (2000).

- [22] N. Yoneyama, T. Sasaki, N. Kobayashi, Y. Ikemoto, and H. Kimura, Phys. Rev. B **72**, 214519 (2005).
- [23] M. S. Mar'enko, C. Bourbonnais, and A.-M. S. Tremblay, Phys. Rev. B **69**, 224503 (2004).